

Electronic Properties of the Semiconductor RuIn_3

D. Bogdanov* and K. Winzer

1. Physikalisches Institut, Georg-August-Universität Göttingen, D-37077 Göttingen, Germany

I.A. Nekrasov

Institute of Electrophysics, Russian Academy of Sciences, 620016, Ekaterinburg, Russia

T. Pruschke

Institut für Theoretische Physik, Georg-August-Universität Göttingen, D-37077 Göttingen, Germany

(Dated: February 6, 2008)

Temperature dependent measurements of the resistivity on RuIn_3 single crystals show a semiconducting behaviour, in contrast to previously published results [1, 2]. In the high temperature range the semiconducting gap was measured to be $0.4 - 0.5$ eV. We observe an anisotropy of the resistivity along [110] and [001] orientations of the tetragonal single crystals. At low temperatures two activation energies of impurities were estimated to 1 meV and 10 meV. The temperature dependence of the specific heat and the band structure calculations provide also a semiconducting behaviour of RuIn_3 .

PACS numbers: 71.20.Lp, 72.20.-i, 71.20.Mq, Nr, 81.10.-h

I. INTRODUCTION

Intermetallic compounds formed by elemental metals with good conductivity are usually metallic conductors as well. A decade ago, R. Pöttgen [2] in a study of the crystal structure and physical properties of RuIn_3 reported on metallic conductivity of this compound. However, for the isostructural compounds FeGa_3 and RuGa_3 electrical resistivity measurements revealed a semiconducting behaviour [3]. Since isostructural gallides and indides of the same group of transition elements have the same number of conduction electrons, the same type of conduction mechanism should be expected. All these compounds crystallise in the tetragonal FeGa_3 structure (space group $P4_2/mnm$) and should show anisotropic electrical properties.

The measurements on RuIn_3 [2] were performed on polycrystalline material obtained by solid state reactions in sealed tantalum tubes, while the measurements on FeGa_3 and RuGa_3 [3] were performed on small unorientated single crystals grown from a Ga-flux. In this article we report on anisotropic transport properties and on caloric properties on RuIn_3 single crystals, which confirm the semiconducting nature of this compound. The experimental results were strongly supported by LDA band structure calculations, which give an indirect band gap of 0.41 eV. Furthermore, the band structure calculations provide a qualitative explanation of the observed transport anisotropy.

II. EXPERIMENTAL

Single crystals of RuIn_3 were grown using the flux method [4] with Indium as reactant and as flux medium. An ingot of Ruthenium ($\cong 0.4$ g) was placed at the bottom of a small Al_2O_3 crucible which was subsequently filled with liquid Indium. The mass ratio of Ru to In used was about 1:20. The crucibles were wrapped by Zr foil and placed in a vertical tube furnace under flowing Ar at atmospheric pressure. Afterwards the furnace was heated to 1150°C and cooled with a rate of 4°C/h to 600°C and below this temperature with a faster rate to 20°C . The crystals were removed from the solidified In by

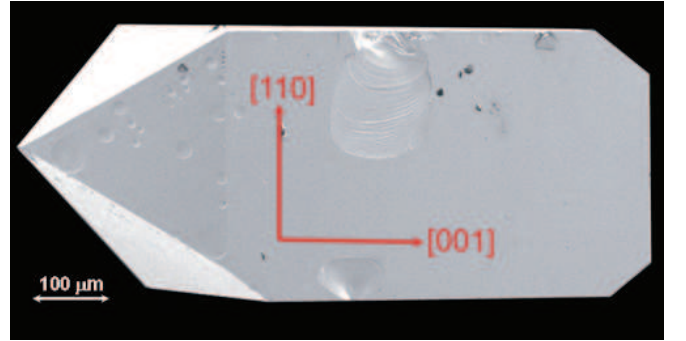


FIG. 1: SEM-picture of a well shaped RuIn_3 single crystal with [110]- and [111]-faces.

heating the crucibles to 200°C and decanting the liquid Indium excess. The single crystals were then etched in dilute HCl to remove the residual In from their surfaces. Well-shaped silvery-gray crystals with sizes of up to 5 mm and masses of about 250 mg were typically obtained. The crystals consist on parallelepipeds with [110]-faces and two pyramidal apices with [111]-faces (see Fig. 1). The different faces of the single crystals were characterised by

*Electronic address: dbogdan@gwdg.de

x-ray diffraction and the orientations were controlled by Laue-diffraction. The stoichiometry of the crystals determined by EDX analysis gives a composition of 25 ± 0.2 at% Ru and 75 ± 0.45 at% In.

To measure the anisotropy of the resistivity the Montgomery-geometry [5] was chosen (see inset Fig. 2). The crystals were cut by spark erosion in cubes with edge lengths of 1.5 mm and supplied with four metallic contacts at the corners of the cubes. In addition measurements of the Hall-coefficient were performed on thin platelets of the same crystals. The measurements of the resistivity were done between 0.06 K and 400 K with a standard Lock-In technique. The measurements of the Hall-coefficient and specific heat were performed between 2 K and 300 K using a Quantum Design PPMS.

III. RESULTS

The temperature dependence of the resistivity obtained by the Montgomery-method on a single crystal of RuIn_3 is shown in Fig. 2. The resistivity ratio

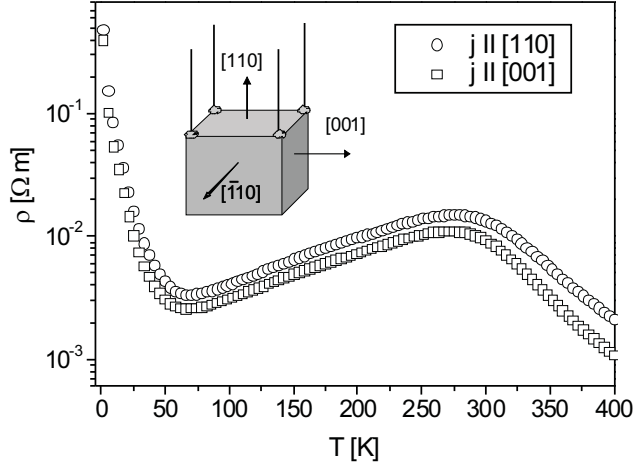


FIG. 2: Temperature dependence of the resistivity of RuIn_3 for different crystallographic directions obtained by the Montgomery-method. Inset shows a single crystal with contacts in Montgomery-geometry.

$\rho[110]/\rho[001]=2.3$ at $T=400$ K shows the anisotropy of the tetragonal crystals. The resistivity increases with decreasing temperature in the range from 400 K to 270 K. In this temperature range the conductivity $\sigma(T)$ can simply be fitted by the equation $\sigma(T) = \sigma_0 \cdot \exp(-E_G/2k_B T)$ for the intrinsic conductivity of a semiconductor. From a plot of $\ln(\sigma/\sigma_0)$ vs. inverse temperature shown in Fig. 3 the gap energy of RuIn_3 can be estimated to $E_{G[110]}=0.455$ eV and $E_{G[001]}=0.513$ eV, respectively.

In the temperature region between 270 K and 120 K the Hall-coefficient of all measured samples is more or less constant and therefore the carrier concentrations were assumed to be constant. In this case the temperature

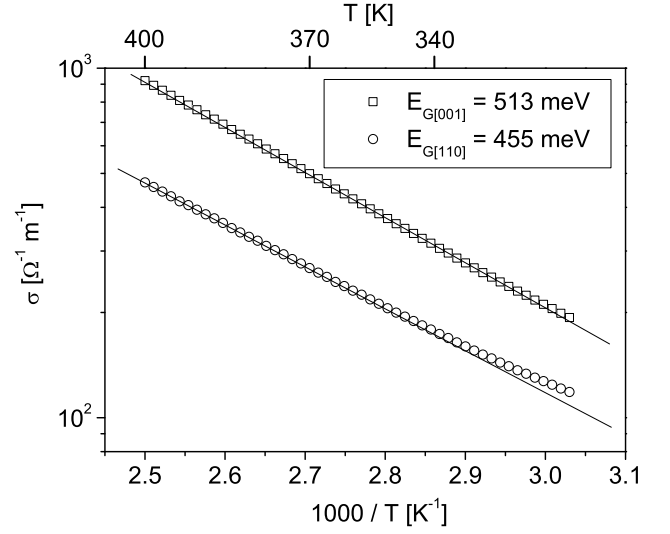


FIG. 3: Conductivity as a function of inverse temperature for different directions in the temperature range of the intrinsic conductivity.

dependence of the conductivity is caused by the temperature dependence of the mobility. If the scattering of the carriers is dominated by acoustic phonons a $T^{-3/2}$ dependence should be observed. Fig. 4 shows the conductivities $\sigma(T)$ for both crystal orientations in a double-logarithmic plot together with a $T^{-3/2}$ straight line which demonstrates that in the range $120 \text{ K} \leq T \leq 250 \text{ K}$ the scattering is dominated by acoustic phonons.

Below 120 K the Hall-coefficient of the RuIn_3 single

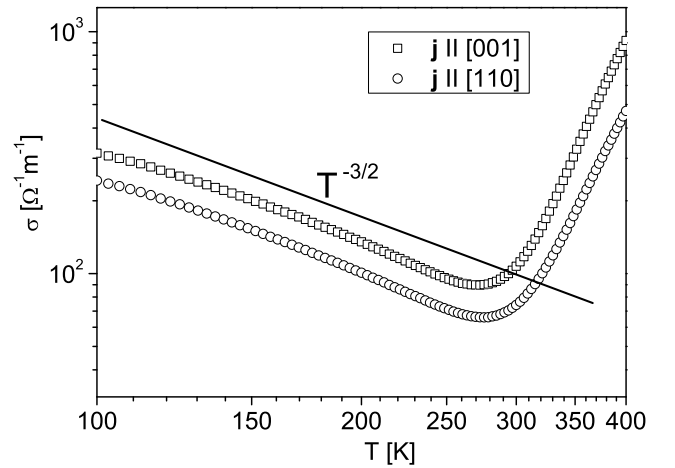


FIG. 4: Conductivity of RuIn_3 vs. temperature for both crystal orientations in a double-logarithmic plot together with a $T^{-3/2}$ -dependence.

crystals is negative and increases with decreasing temperature. In this temperature range the conductivity diminishes caused by the freezout of the extrinsic electrons and holes. Due to the different binding energies of the

extrinsic carriers and the temperature dependence of the corresponding mobilities the temperature dependence of $R_H(T)$ is rather complex. In a two band model with electrons and holes the Hall-coefficient is given by

$$R_H(T) = \frac{1}{e} \cdot \frac{n_h \mu_h^2 - n_e \mu_e^2}{(n_h \mu_h + n_e \mu_e)^2} \quad (1)$$

with the concentrations n_h, n_e and the mobilities μ_h, μ_e of the holes and the electrons. From the measured conductivity $\sigma(T)$ and the Hall-coefficient $R_H(T)$ the product

$$R_H(T) \cdot \sigma^2(T) = e \cdot (n_h \mu_h^2 - n_e \mu_e^2) \quad (2)$$

can be obtained, which temperature dependence is easier to interpret. In Fig. 5 the product $R_H(T)\sigma^2(T)$ is given as a function of temperature. At low temperatures ($T < 20$ K) the value of $|R_H(T)\sigma^2(T)|$ is very small since most of the carriers are frozen at their impurity sites. $|R_H(T)\sigma^2(T)|$ steeply increases above 50 K reaching a maximum at about 90 K. Since the sign of $R_H(T)\sigma^2(T)$ is negative the increase is caused by the thermal activation of electrons from donors with a small activation energy E_D . Above 90 K $|R_H(T)\sigma^2(T)|$ decreases strongly

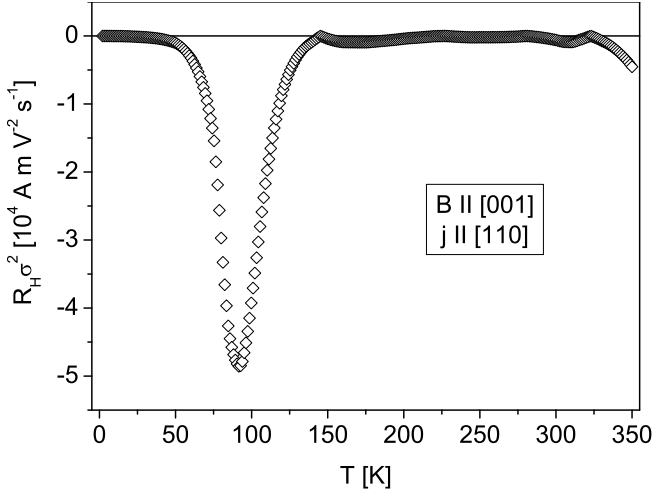


FIG. 5: The product $R_H(T)\sigma^2(T)$ as a function of temperature for the magnetic field $\mathbf{B} \parallel [001]$ and the current density $\mathbf{j} \parallel [110]$.

reaching $R_H(T)\sigma^2(T) = 0$ at about 150 K. The decrease of $|R_H(T)\sigma^2(T)|$ in the range $90 \text{ K} \leq T \leq 150 \text{ K}$ will be produced by the thermal activation of holes from acceptors with a larger activation energy E_A . It should be noted that $|R_H(T)\sigma^2(T)|$ is comparably small in the whole temperature range $150 \text{ K} \leq T \leq 300 \text{ K}$. This could be a hint to the fact, that both kinds of carriers originate from the same type of structural defects. The activation energies E_D and E_A can be obtained from the plot of $\ln(\sigma/\sigma_0)$ vs. inverse temperature T^{-1} in the temperature range $5 \text{ K} \leq T \leq 50 \text{ K}$, which is given in Fig. 6. Typical values obtained for the activation energies on different

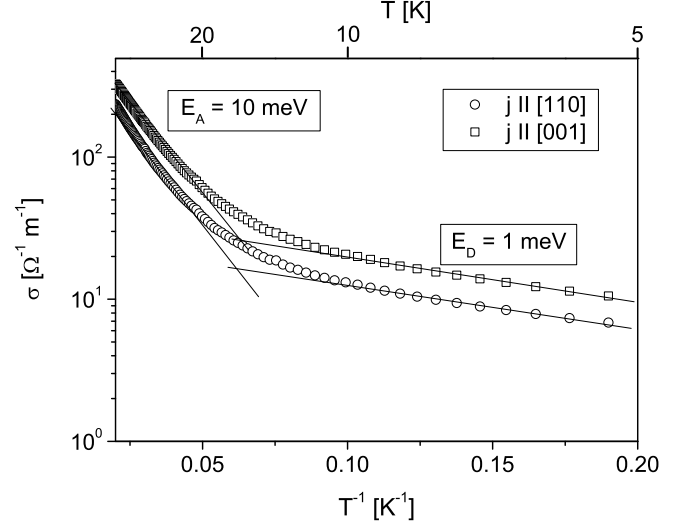


FIG. 6: Conductivity as a function of inverse temperature for different crystal orientations in the temperature range $5 \text{ K} \leq T \leq 50 \text{ K}$.

single crystals are $E_D = 1.0\text{--}1.5 \text{ meV}$ for the donors and $E_A = 10 \text{ meV}$ for the acceptors. In the temperature range $T > 320 \text{ K}$ the quantity $R_H(T) \cdot \sigma^2(T)$ becomes negative again. In this regime intrinsic conductivity dominates and $n_h = n_e = n_i$. From $R_H \cdot \sigma^2 = en_i(\mu_h^2 - \mu_e^2) < 0$ it follows $\mu_e > \mu_h$, which in turn implies $m_e^* < m_h^*$. The interpretation of this observation will be given in connection with band structure calculations.

The specific heat of RuIn_3 , measured on a single crystal with a mass of $m \approx 25 \text{ mg}$ is given in Fig. 7. $C(T)$ shows the typical temperature dependence of a semiconductor or an insulator in the temperature range $2 \text{ K} \leq T \leq 300 \text{ K}$ with a value of $100 \text{ J mol}^{-1} \text{ K}^{-1}$ at 300 K . The inset of Fig. 7 shows the low temperature data ($2 \text{ K} \leq T \leq 4 \text{ K}$) in a C/T vs. T^2 plot. The extrapolation to $T = 0 \text{ K}$ goes through the origin, and indicates that the contribution of the carriers is very small. This fact corroborates the semi-conducting behaviour of our transport measurements. The value of the slope is $A = 4.5 \cdot 10^{-4} \text{ J mol}^{-1} \text{ K}^{-4}$. From this result the Debye-temperature $\Theta_D = \left(\frac{12\pi^4 N k_B}{5A} \right)^{1/3}$ of RuIn_3 can be calculated to $\Theta_D = 258 \text{ K}$.

IV. BAND STRUCTURE CALCULATION

State-of-the-art electronic structure calculations from first principles are based on density functional theory (DFT) within the local density approximation (LDA). To calculate the electronic structure of RuIn_3 , the TB-LMTO-ASA package v.47 (Tight Binding, Linear Muffin-Tin Orbitals, Atomic Sphere Approximation) [6] was used with experimentally obtained values of the lattice constants ($a = b = 7.003 \text{ \AA}$, $c = 7.247 \text{ \AA}$, tetragonal space group $P4_2/mnm$ #136 [2]). The Ru sites occupy

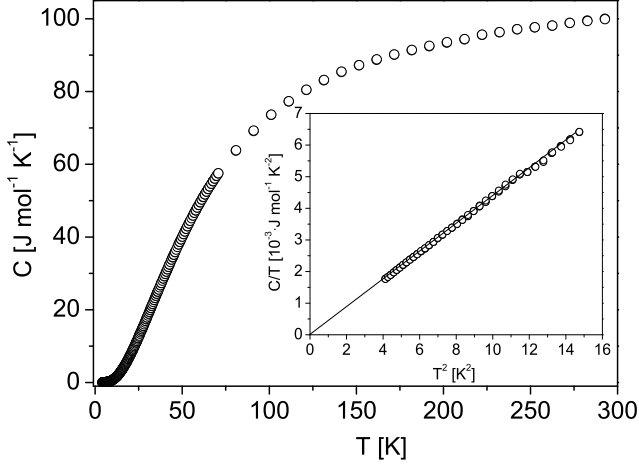


FIG. 7: Specific heat of RuIn_3 in the temperature range $2 \text{ K} \leq T \leq 300 \text{ K}$. Inset: Plot of C/T vs. T^2 in the low temperature range $2 \text{ K} \leq T \leq 4 \text{ K}$.

4f Wyckoff positions ($x = 0.3451$, $y = 0.3451$, $z = 0$) and there exist two crystallographically inequivalent In sites at positions 4c for In1 ($x = 0$, $y = 0.5$, $z = 0$) and 8j for In2 ($x = 0.15547$, $y = 0.15547$, $z = 0.26224$). The crystal structure is presented in Fig. 8. Atomic spheres

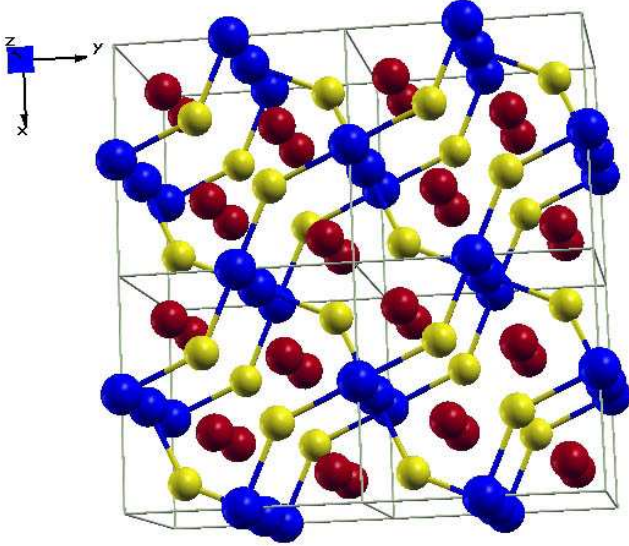


FIG. 8: Crystal structure of RuIn_3 . Red-In1 sites, blue-In2 sites, yellow-Ru sites.

radii were chosen to be $R(\text{Ru})=2.88 \text{ a.u.}$, $R(\text{In1})=2.92 \text{ a.u.}$ and $R(\text{In2})=2.97 \text{ a.u.}$. The orbital basis consists of 5s, 5p, 4d muffin-tin orbitals for Ru and 5s, 5p for In1 and In2 sites. To fill the space of the unit cell several empty (without nuclei charge) atomic spheres were introduced. The calculations were performed with 405 irreducible $\mathbf{k}$ -points ($16 \times 16 \times 16$ spacing) in the first Brillouin zone.

In Fig. 9 we present the densities of states (DOS)

obtained within the LMTO method. The upper panel displays the total DOS with an energy gap of 0.41 eV. The individual contributions of Ru 5s, 5p and 4d states and the 5s, 5p states of both In sites to the total DOS are shown in the middle and lower panels of Fig. 9, respectively. By comparing the total and partial DOS, one

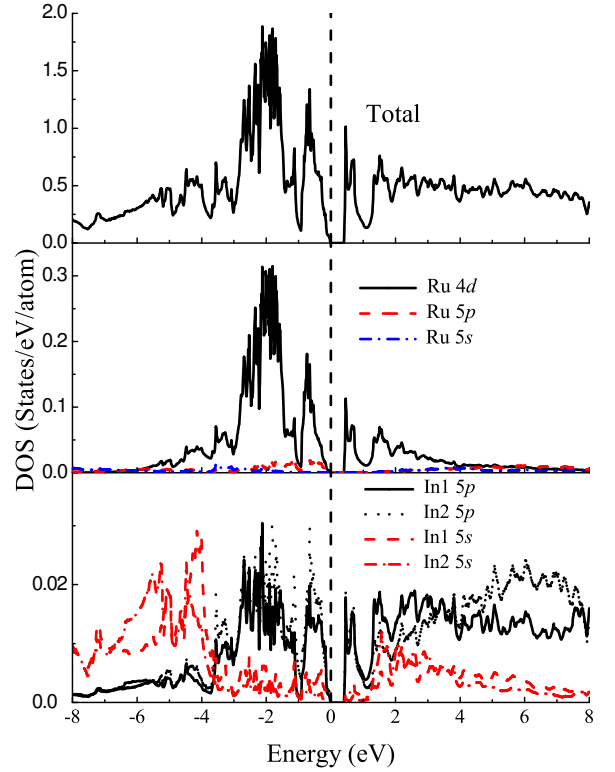


FIG. 9: LDA calculated densities of states for RuIn_3 . The upper panel shows total DOS. The middle panel displays Ru 4d (full line), Ru 5p (dashed line) and Ru 5s (dotted line) states. The lower panel contains In1 5p (full line), In2 5p (long dashed line), In1 5s (dotted line) and In2 5s (dashed line) states. Fermi level corresponds to zero.

can identify several evident features. The energy range below -4.5 eV is dominated by In1(2) 5s states. In the energy interval $-4.5 \dots 2 \text{ eV}$ one observes that the 5p states of In1 and In2 hybridise relatively strongly with Ru 4d states. Finally, above 2 eV there are predominantly In 5p states (see lower panel, Fig. 9).

The observed anisotropy of transport properties with different resistivities along ab and c directions is quite generally consistent with the simple tetragonal crystal structure of the compound. In order to qualitatively explain why the ab resistivity is larger than the one along c we first note that the properties of hole transport will be determined by the top of the valence band located at $\mathbf{k}$ -point $(0.48, 0.48, 0.48)$ of the RA high symmetry direction (see Fig. 10), because the energy gap is much larger than the experimental temperature and there are

no other bands below this one within the interval of energies corresponding to the experimental temperature.

From the LDA band structure analyses one can conclude that the orbitals contributing to the top of the valence band along the RA high symmetry direction in Fig. 10 can be separated into those lying in the XY plane and those along the Z-axis. The former are superpositions of In2 5p_x, 5p_y and Ru 4d_{xz}, 4d_{yz} orbitals, the latter

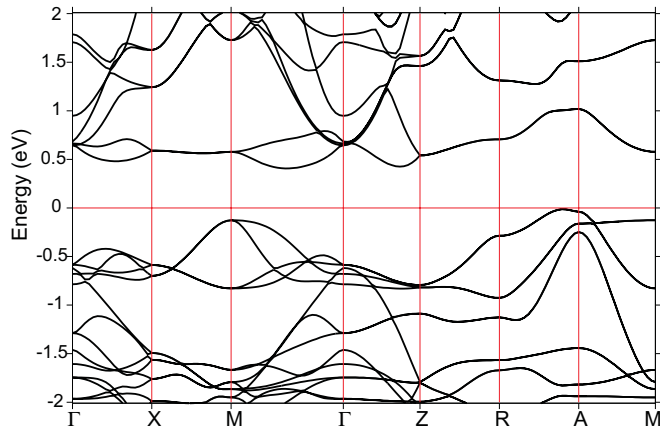


FIG. 10: Band structure of RuIn₃ in the vicinity of the Fermi level calculated within standard DFT/LDA. The Fermi level corresponds to zero.

obtained from In1 5p_z and again Ru 4d_{xz}, 4d_{yz} orbitals, and a small In2 5p_z contribution [7]. There is also an In1 5s contribution to the top of the valence band which is anisotropic. Contributions of other symmetries are negligible.

The strongest orbital overlap is obtained for nearest neighbours. In the XY-plane these nearest neighbours are In2-Ru and Ru-Ru, In1 sites do not have nearest neighbours in the XY-plane. Along the Z-axis nearest neighbours are Ru-In1 and In1-In2. Together with the previous classification of the orbitals contributing to the top of the valence band we can have In2-Ru *pd* π hybridisation (In2 5p_z and Ru 4d_{xz} and 4d_{yz}) and Ru-Ru *dd* δ hybridisation (Ru 4d_{xz}-4d_{xz}, Ru 4d_{yz}-4d_{yz}) [8] in the XY-plane. These two types of hybridisation are known to be quite weak [9]. Along the Z-axis the possible hybridisation are Ru-In1 *sd* σ (Ru 4d_{xz}, 4d_{yz} and In1 5s), In1-In2 *sp* σ (In1 5s and In2 5p_x, 5p_y, 5p_z) and *pp* σ (In1 5p_z and In2 5p_z), which in principle are stronger [9] than the ones found for the XY-plane, thus qualitatively explaining the better conductivity along the Z-axis.

A similar argumentation can be applied to the electron transport dominated at low temperatures by the bottom of the conduction band in the middle of the ΓM direction.

Since the angles between bonds are not ideal in RuIn₃ (90° or 180°), there will of course be other types of hybridisation. Furthermore, next nearest neighbour hoppings will contribute as well. All these effects will further reduce the anisotropy and lead to three dimensional behaviour despite the layered structure of RuIn₃. Given all these partially compensating effects a final quantitative

answer on the size of the anisotropy thus surely requires more detailed numerical investigations.

The band structure of RuIn₃ given in Fig. 10 shows a maximum of the valence band along RA in the Brillouin zone near A. The calculated effective hole mass is $m_h \approx 1.2m_0$. The minimum of the conduction band is formed by a flat band along ΓM with a large effective electron mass $m_{e1} \approx 2.6m_0$. Therefore in the intrinsic regime the quantity $R_H \cdot \sigma^2$ should be positive in contrast to the observed high temperature behaviour in Fig. 5. However, the band structure shows a second minimum of the conduction band along ΓZ near Z with a substantial smaller effective mass of $m_{e2} \approx 1.1m_0$. The energy difference between the two conduction band minima is only 20meV, which is smaller as the thermal energy $k_B T$ at $T \geq 300K$. Hence, the small effective electron mass m_{e2} of the conduction band minimum near Z with the implication $\mu_{e2} > \mu_h$ is responsible for the negative sign of $R_H \cdot \sigma^2$ observed by the experiments in the intrinsic range.

V. SUMMARY

Measurements of the resistivity and of the Hall-coefficient of RuIn₃ single crystals identify this compound as a semiconductor with a gap energy of $E_G = 0.46$ -0.51eV, in contrast to previously published results, which report on metallic conductivity. The calculated band structure based on the density functional theory gives a similar value of $E_G = 0.41$ eV.

The experimentally observed slight anisotropy of the resistivity $\rho[110] > \rho[001]$ can qualitatively be explained by a theoretical symmetry analyses which predict a better conductivity along the *c*-axis of the tetragonal compound. The negative sign of the Hall-coefficient in the intrinsic region can also be explained by the calculated conduction band structure with two energetically nearly equivalent minima but with very different effective electron masses.

In the extrinsic range at low temperatures a small activation energy for electrons from donors of $E_D = 1.0$ -1.5meV and a larger activation energy for holes from acceptors of $E_A = 10$ meV were determined from the transport measurements. Both kinds of extrinsic carriers seems to originate from the same type of structural defects, since $R_H \cdot \sigma^2$ is nearly zero in a large temperature range $150K < T < 320K$. The low temperature data of the specific heat show a negligible contribution of charge carriers and corroborate the semiconducting nature of RuIn₃.

Acknowledgments

IN thanks A. Postnikov for many helpful discussions. This work was supported in part by RFBR grants 05-02-16301 (IN), 05-02-17244 (IN), 06-02-90537 (IN), by the

joint UrO-SO project (IN), and programs of the Presidium of the Russian Academy of Sciences (RAS) "Quantum macrophysics" and of the Division of Physical Sciences of the RAS "Strongly correlated electrons in semiconductors, metals, superconductors and magnetic materials" and the by the DFG through the collaborative research grant SFB 602 (TP,IN). I.N. acknowledges support

from the Dynasty Foundation and International Center for Fundamental Physics in Moscow program for young scientists and also from the grant of President of Russian Federation for young PhD MK-2242.2007.02, and thanks the Faculty of Physics of the Georg-August University of Göttingen for its hospitality.

-
- [1] R.B. Roof, Z. Fisk, and D.L. Smith, *Powder Diffraction* **1**, 20 (1986).
 - [2] R. Pöttgen, *J. Alloys and Compounds* **226**, 59 (1995).
 - [3] U. Häussermann, M. Boström, P. Viklund, Ö. Rapp, and T. Björnängen, *J. Solid State Chemistry* **165**, 94 (1992).
 - [4] see for instance: P.C. Canfield, and Z. Fisk, *Phil. Mag. B* **70**, 1117 (1992) and references therein.
 - [5] H.C. Montgomery, *J. Appl. Phys.* **42**, 2971 (1971).
 - [6] O.K. Andersen, O. Jepsen, and D. Glözel, in *Highlights of Condensed-Matter Theory*, edited by F. Bassani, F. Fumi, and M.P. Tosi (North-Holland, New York, 1985); O.K. Andersen and O. Jepsen *Phys. Rev. Lett.* **53**, 2571 (1984).
 - [7] Since RuIn_3 cristallizes in a tetragonal structure without distortions, there is no need to introduce a local coordinate system for each particular atom to properly resolve the orbitals with respect to their magnetic quantum number.
 - [8] J. C. Slater and G. F. Koster, *Phys. Rev.* **94**, 1498 (1954).
 - [9] O. K. Andersen, W. Klose and H. Nohl, *Phys. Rev. B* **17**, 1209 (1978).